

מכון ויצמן למדע

WEIZMANN INSTITUTE OF SCIENCE



Control of Electrons' Spin Eliminates Hydrogen Peroxide Formation During Water Splitting

Document Version:

Accepted author manuscript (peer-reviewed)

Citation for published version:

Mtangi, W, Tassinari, F, Vankayala, K, Jentsch, AV, Adelizzi, B, Palmans, ARA, Fontanesi, C, Meijer, EW & Naaman, R 2017, 'Control of Electrons' Spin Eliminates Hydrogen Peroxide Formation During Water Splitting', *Journal of the American Chemical Society*, vol. 139, no. 7, pp. 2794-2798.
<https://doi.org/10.1021/jacs.6b12971>

Total number of authors:

9

Digital Object Identifier (DOI):

[10.1021/jacs.6b12971](https://doi.org/10.1021/jacs.6b12971)

Published In:

Journal of the American Chemical Society

License:

Unspecified

General rights

@ 2020 This manuscript version is made available under the above license via The Weizmann Institute of Science Open Access Collection is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognize and abide by the legal requirements associated with these rights.

How does open access to this work benefit you?

Let us know @ library@weizmann.ac.il

Take down policy

The Weizmann Institute of Science has made every reasonable effort to ensure that Weizmann Institute of Science content complies with copyright restrictions. If you believe that the public display of this file breaches copyright please contact library@weizmann.ac.il providing details, and we will remove access to the work immediately and investigate your claim.

Control of Electrons' Spin Eliminates Hydrogen Peroxide Formation During Water Splitting

Wilbert Mtangi,[†] Francesco Tassinari,[†] Kiran Vankayala,[†] Andreas Vargas Jentsch,[‡] Beatrice Adelizzi,[‡] Anja R. A. Palmans,[‡] Claudio Fontanesi,[§] E. W. Meijer,^{*,‡} and Ron Naaman^{*,†}


[†]Department of Chemical Physics, Weizmann Institute of Science, Rehovot 76100, Israel

[‡]Institute for Complex Molecular Systems, Eindhoven University of Technology, 5600 MB Eindhoven, The Netherlands

[§]Department of Engineering, University of Modena and Reggio Emilia, Via Vivarelli 10, 41125 Modena, Italy

S Supporting Information

ABSTRACT: The production of hydrogen through water splitting in a photoelectrochemical cell suffers from an overpotential that limits the efficiencies. In addition, hydrogen-peroxide formation is identified as a competing process affecting the oxidative stability of photoelectrodes. We impose spin-selectivity by coating the anode with chiral organic semiconductors from helically aggregated dyes as sensitizers; Zn-porphyrins and triarylamines. Hydrogen peroxide formation is dramatically suppressed, while the overall current through the cell, correlating with the water splitting process, is enhanced. Evidence for a strong spin-selection in the chiral semiconductors is presented by magnetic conducting (mc-)AFM measurements, in which chiral and achiral Zn-porphyrins are compared. These findings contribute to our understanding of the underlying mechanism of spin selectivity in multiple electron-transfer reactions and pave the way toward better chiral dye-sensitized photoelectrochemical cells.

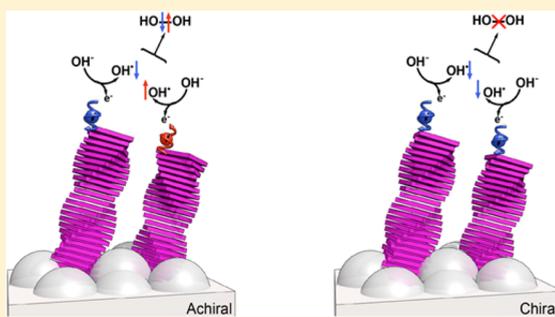

INTRODUCTION

Since it has no carbon, has the highest specific enthalpy of combustion of any chemical fuel, and generates water as its oxidation product, hydrogen has been referred to as the fuel of the future.¹ Although significant progress has been made over the past decades,² the generation of hydrogen by green, sustainable methods on a global scale remains a future goal.^{3–8} While technologies exist for the electrolysis of water and photoelectrochemical generation of hydrogen from water,⁹ the processes involve significant overpotentials and the formation of peroxides and superoxide radical byproducts. These byproducts have the tendency to adsorb onto the photocatalyst, poisoning it, thereby reducing its stability and lifetime.¹⁰ Although specific catalysts are proposed to use the peroxides as intermediates,¹¹ this path requires higher voltage. Therefore, a fundamental solution for the off-pathway products is essential. Water splitting is a four-electron process that generates hydrogen molecules having singlet ground states and oxygen molecules having triplet ground states. Commonly, the artificial water splitting process requires an overpotential of about 0.6 V vs normal hydrogen electrode (NHE), to drive the oxygen evolution reaction.^{12–14} The importance of electron-spin correlation of electrons in generating O₂ has been debated for biological photosynthesis. Particularly the chemistry associated with the oxygen evolution reaction in photosystem II has been examined.^{15–17} Nevertheless, the details of the mechanism of the O=O bond formation remain unre-

solved.^{18–20} Although the spin state of the electrons involved is rarely discussed in works exploring artificial photosynthesis, recent theoretical studies suggest that the overpotential required to split water is linked to restrictions on the electrons' spin in generating a ground state triplet oxygen molecule.^{21,22} In recent experimental work, it has been shown that when the anode in the water splitting cell is coated with chiral molecules, the overpotential is reduced.²³ It has been proposed that the effect is due to spin filtering occurring when electrons are conducted through chiral systems.²⁴ However, and very importantly, the possible role of the spin control in suppressing the formation of hydrogen peroxide has not been discussed nor experimentally addressed.

Here, we hypothesize that hydrogen peroxide is produced due to uncontrolled spin alignment²⁵ and greatly contributes to the high overpotentials. Hence, controlling the spin state of the electronic potential on which the reaction occurs should result in more efficient oxygen production and limited production of hydrogen peroxide. Although we do not strive here to present the highest production of hydrogen and oxygen—optimizing the cells is ongoing—the results presented show an unprecedented control of chemical kinetics through spin selection.

Received: December 17, 2016

Published: January 30, 2017

72 ■ RESULTS AND DISCUSSION

73 To first control the spin state, the ITO anode in the
74 photoelectrochemical cell was coated with two families of
75 organic semiconductors, Zn porphyrins and tri(pyrid-2-yl)-
76 amine trisamide, TPyA, both in their chiral (using enantiomerically
77 pure side chains) and achiral (using achiral side chains)
78 versions (Figure 1A,B). By modifying the side chains of the

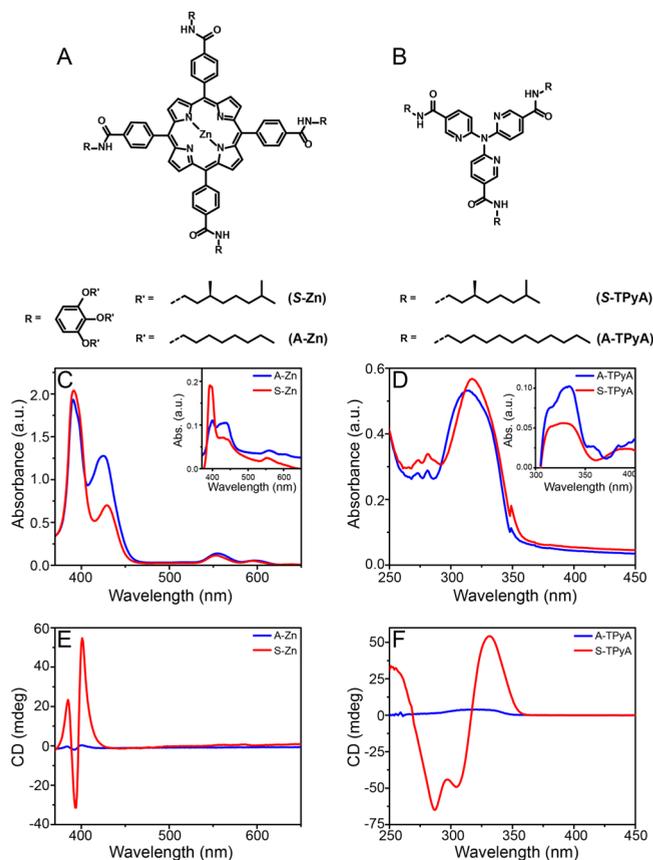


Figure 1. Molecules used as photosensitizer and their supramolecular aggregation. (A) The chiral and achiral Zn porphyrins, (C and E) their absorption spectra and CD spectra of the aggregated state in solution (1.7×10^{-5} M in methylcyclohexane) and when adsorbed on the surface (inset) (B) the chiral and achiral TPyA, (D and F) their absorption and CD spectra of the aggregated state in solution and when adsorbed on the surface (inset). The red curves represent the chiral molecules, while the blue represent the achiral ones.

79 molecules, we control the resulting helical supramolecular
80 assemblies into either a bias for one helical sense or a racemic
81 mixture of both helical senses, respectively. Thus, in the present
82 study, electrons are transmitted into the TiO_2 substrate through
83 the same molecular system, which only differs in its molecular
84 organization; either one helical sense or a mixture of both. In
85 the case of Zn-porphyrins, the 390 nm Soret band confirms the
86 formation of helical supramolecular structures in solution
87 (Figure 1C),^{26,27} which are retained when transferred to the
88 surface (inset of Figure 1C). In a similar manner, the 317 nm
89 band is indicative of the formation of a supramolecular
90 assembly for the TPyA molecules. For both molecules, the
91 chiral analogues show a strong CD response which is not
92 observed in the achiral version (Figure 1E,F). The achiral
93 molecules most probably aggregate in equal amounts of left-

and right-handed helices (racemic mixture), while the chiral
94 molecules prefer one of both only.

Magnetic conducting atomic force microscopy (mc-AFM)
96 measurements were conducted to verify the spin selectivity of
97 electron transmission through the Zn-porphyrin stacks.²⁸
98 Figure 2B shows the dependence of the current on the
99

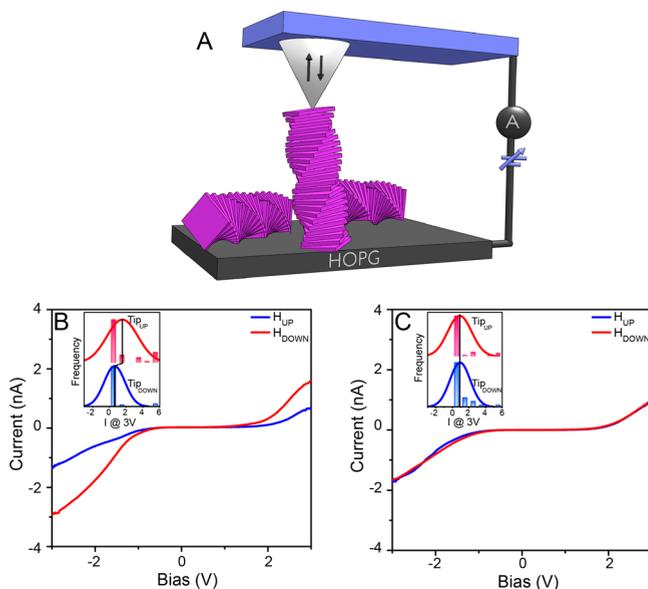


Figure 2. Magnetic conducting atomic force microscopy (mc-AFM) measurements on stacks of chiral and achiral Zn-porphyrins. (A) The experimental setup. The current as a function of the applied voltage obtained from the chiral (B) and achiral (C) Zn-porphyrin molecules. The insets show corresponding histograms of currents obtained at 3 V for the two opposite magnetic orientations of the tip.

orientation of the magnetic field at the tip of the mc-AFM for 100
the stack of chiral porphyrins, which confirms that one spin is 101
preferred over the other. It is important to realize that the ratio 102
between the two spin currents is affected by the nonideal spin 103
injection from the magnetic tip. Since the spin polarization of 104
the tip is only about 35%, it means that the actual spin filtering 105
of the molecular system is about 4:1, in other words only about 106
20% of the electrons conducted through the chiral molecular 107
aggregates in this experiment have the “wrong” spin. From 108
Figure 2C, it can be observed that for the achiral compounds, 109
the magnitude of the current measured as a function of applied 110
bias does not depend on the orientation of the magnetic field; 111
hence the conduction through this system with equal amount 112
of right and left handed helices is not spin specific. These 113
results indicate that the supramolecular structures formed from 114
the chiral porphyrins can efficiently filter spins and are 115
consistent with previous reports in which chiral molecules 116
have been observed to be good spin filters.²⁹ 117

Next, photoelectrochemical measurements were conducted 118
in a three-electrode cell, with the Ag/AgCl (saturated KCl) as 119
the reference electrode and a Pt wire as the cathode (Figure 3). 120
A 0.1 M Na_2SO_4 (pH = 6.56) aqueous solution was used as the 121
electrolyte. TiO_2 substrates fabricated and functionalized as 122
outlined in the Supporting Information, were used as 123
photoanodes. In these cells, the magnitude of the measured 124
current is correlated with the amount of oxygen bubbles 125
produced at the anode and hydrogen bubbles at the cathode. 126

Higher photocurrent densities are observed for photo- 127
electrodes functionalized with helical aggregates of chiral 128

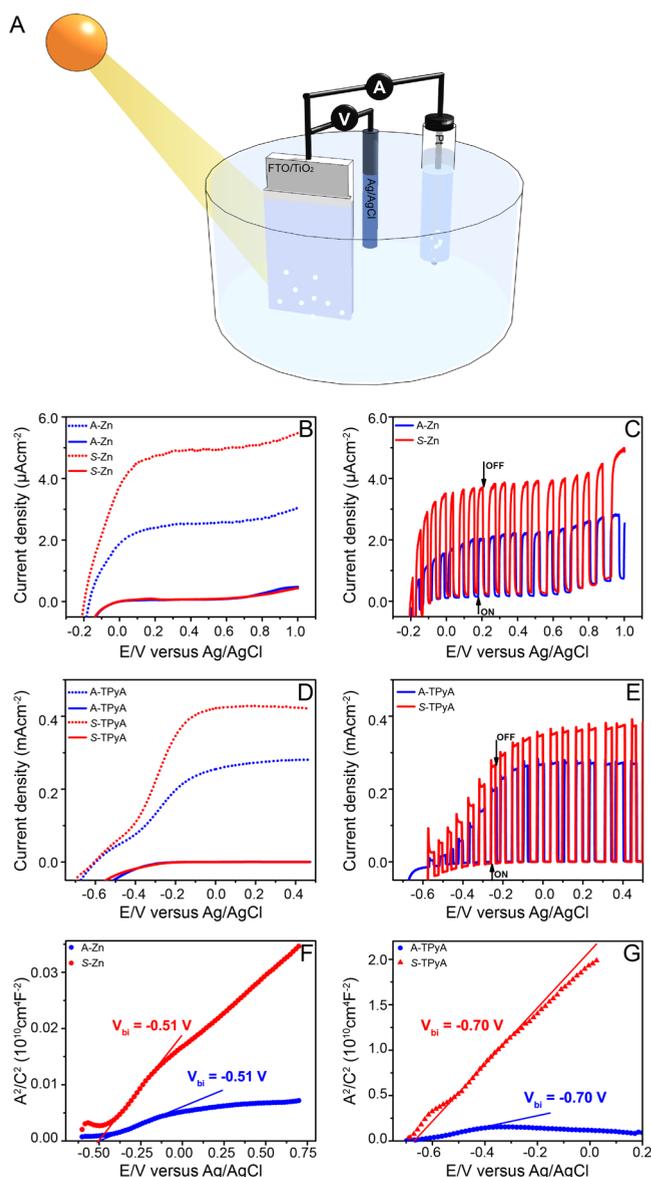


Figure 3. Photoelectrochemical cell and the current density as a function of the potential. In A, a schematic representation of the photoelectrochemical cell. The potential is given vs the Ag/AgCl electrode, when the TiO₂ electrode is coated with self-assembled achiral (blue lines) or chiral (red lines) molecules. In (B) and (C), Zn-porphyrins were used while in (D) and (E), TPYA molecules were employed. The measurements were performed in the dark (solid lines) and under illumination (dotted lines). In (C) and (E) measurements were performed while chopping the light. All measurements were performed at a scan rate of 10 mVs⁻¹. The flat-band potentials in the dark for Zn-porphyrin and TPYA molecules were obtained from Mott–Schottky plots (F and G, respectively) at a frequency of 1.99 kHz and oscillation voltage of 20 mV.

illumination of the cell. The activity of the photoelectrodes is known to depend strongly on their electronic properties, therefore Mott–Schottky measurements were performed to characterize the electronic properties of TiO₂ electrodes modified with aggregates of Zn porphyrin and TPYA molecules. A flat-band potential, V_{bi} of -0.51 V vs Ag/AgCl was obtained in the dark for both the chiral and the achiral Zn-porphyrins (Figure 3E), while a value of approximately -0.70 V vs Ag/AgCl was obtained for the TPYA molecules (Figure 3F), an indication that the difference in the photocurrents, for chiral and achiral species, is not related to the modification of the electronic properties of the photoelectrodes. Thus, the differences in the photocurrents must be attributed to the chirality of the molecules.

After showing the difference in water splitting for the chiral versus racemic aggregates, the beneficial effect of electrons' spin control is highlighted by its effect on hydrogen peroxide formation. An indirect quantification of the H₂O₂ produced during photoelectrochemical water splitting was conducted. Spectrophotometric titration of the used electrolytes were performed using o-tolidine as redox indicator.^{31,32} The amount of peroxide formed has been quantified through Ellms-Hauser method calibrating the system with commercial H₂O₂ (see Figures S12–S14). In the presence of H₂O₂, a yellow color appears with an absorption peak at about 436 nm. This peak is characteristic for the complete two-electron oxidation product of o-tolidine formed by the reaction with hydrogen peroxide.³³

The electrolyte obtained from the bare TiO₂ and electrodes functionalized with achiral dyes showed the characteristic peak at 436 nm, indicating the production of H₂O₂ during water oxidation (see Table S1). Fascinatingly, no detectable amount of hydrogen peroxide was observed for electrodes with the chiral molecules physisorbed (Figure 4A,B). Noticeably, after 40 min of irradiation, 43 ± 5 mmolL⁻¹ of hydrogen peroxide have been produced with the achiral Zn-porphyrin functionalized system while nondetectable levels of peroxide have been found using the chiral analogue. The TPYA functionalized systems show low absorbance intensity at 436 nm. The relatively low level of H₂O₂ in the case of A-TPYA may result for performing the electrochemistry measurements under illumination with UV light, which might have led to the disproportionation of the produced peroxide before titration. However, also in this case, much less H₂O₂ is produced with the chiral molecules (S-TPYA) than with the achiral ones (A-TPYA). Additional evidence is obtained by using achiral 3-mercaptopropionic acid and the chiral oligopeptide [(COO-H)–(Ala-Aib)₇–NH–(CH₂)₂–SH] (see Figure S13). Only the latter decreases the H₂O₂ production. These results further indicate that the observed elimination of the hydrogen peroxide production is general for all chiral molecules.

The results presented here in the quantification of H₂O₂ production together with the electrochemistry data show a strong correlation between the overpotential, the formation of H₂O₂, and the electron's spin alignment control. During water splitting, two OH⁻ species must combine to form molecular oxygen in its triplet ground state. In the process, an electron from each OH⁻ is transferred to the anode. This leaves the two OH[•] radicals in their doublet ground state, namely each OH[•] has one unpaired electron. When there is no spin control and the interaction electronic potential has a singlet character, the formation of H₂O₂ is possible (Figure 4). However, when the electron's spins are aligned in a parallel fashion, the two electrons interact on the triplet potential surface which

129 molecules with preferred helicity, compared to those coated
130 with racemic aggregates of achiral ones. This is remarkable,
131 given that the chemical compositions of the chiral and achiral
132 molecules for the two sets used in this study are very similar,
133 except for the stereocenter present in the chiral molecules. In
134 general, the magnitude of the photocurrents obtained with the
135 Zn-porphyrins are typically low, as has also been observed by
136 Moore et al.³⁰ With the TPYA molecules, the photocurrent
137 densities are reasonably high, since UV light is used for

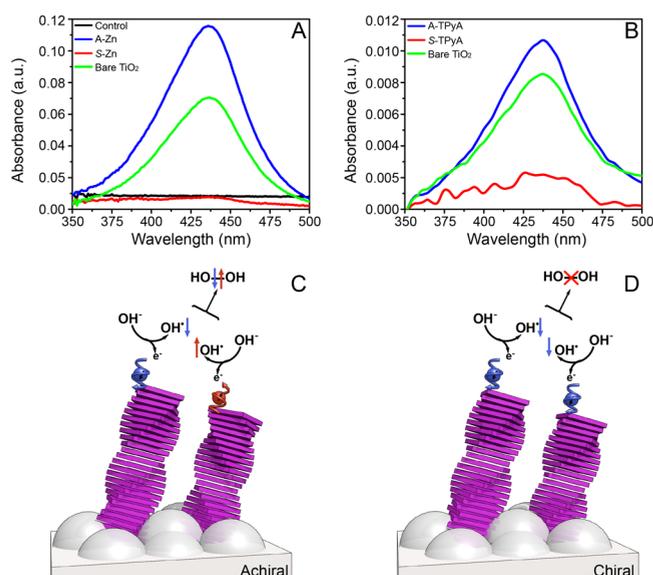


Figure 4. Control of the hydrogen peroxide production. UV-vis absorption spectra from the titration of the used electrolyte (Na_2SO_4) with *o*-tolidine of bare TiO_2 and TiO_2 electrodes coated with (A) self-assembled Zn-porphyrins of either achiral (A-Zn) or chiral (S-Zn) and (B) TPyA molecules. The control refers to the titration of unused Na_2SO_4 with *o*-tolidine. (C) When the electrons transfer to the anodes is non spin specific the spins of the unpaired electrons on the two OH^\bullet are aligned antiparallel, hence the interaction between the two OH^\bullet is on a singlet surface that correlates with the production of hydrogen peroxide (H_2O_2). (D) When the electron transfer to the anode is spin specific, the spins of the two electrons are aligned parallel to each other, hence the two OH^\bullet interact on a triplet surface that forbids the formation of H_2O_2 and facilitates the production of oxygen in its ground state.

201 correlates with the formation of the ground state molecular
202 oxygen and on which the formation of H_2O_2 is symmetry
203 forbidden.

204 The formation of oxygen and hydrogen peroxide are
205 anticorrelated; i.e., the formation of one is coming at the
206 expense of the other. This is what the present results indicate.
207 However, it is difficult to draw a quantitative relation between
208 the change in the current and the hydrogen peroxide formation,
209 since the change in the current reflects the change in the
210 threshold potential for the process while the decrease in the
211 hydrogen peroxide formation is an indication for the extent of
212 spin polarization. Of course, the substrate (the catalyst) may
213 induce spin-orbit coupling that will mix the spin states of the
214 OH radical. However, for TiO_2 and other relatively light
215 materials, the spins of physisorbed molecules are expected to be
216 conserved, as observed by XPS studies.³⁴ Note that substrate-
217 induced spin-orbit coupling may explain the low overpotential
218 observed for some oxides,^{35,36} magnetic catalysts or catalysts
219 made from heavy atoms. For these systems, the side products
220 are not significantly suppressed. Indeed, no investigations were
221 performed in the past aimed at controlling the formation of
222 H_2O_2 .

223 CONCLUSIONS

224 The experimental results observed in the current study provide
225 new insights into the mechanism behind oxygen formation in
226 the oxygen evolution reaction and provide a new path for
227 improving the efficiency of the water splitting process.
228 Obviously, much work has to be done to optimize the system

with other and more effective chiral dyes, chiral semi-
conductors, and chiral catalysts, but a proof-of-principle to
make another counterintuitive approach is presented. The
control of electrons' spin in the chemical kinetics during the
photochemical water splitting will also rejuvenate the field of
magnetic field effects in chemical kinetics and related
phenomenon as reviewed by Steiner and Ulrich many years
ago, following the discovery and understanding of electron spin
polarized phenomena during chemical reactions. This is the
more of importance due to the recent interest in photoredox
catalysis in organic chemistry with exciting enantioselectivities.
In addition, the work points to the importance of chirality and
spin selectivity in multiple electron reactions in biology.

242 ASSOCIATED CONTENT

243 Supporting Information

The Supporting Information is available free of charge on the
ACS Publications website at DOI: 10.1021/jacs.6b12971.

Experimental details, synthesis, preparation, and func-
tionalization of TiO_2 electrodes. Additional details SEM,
spectroscopic data, photoelectrochemical measurements,
AFM mc-AFM, and spectrophotometric titration of
 H_2O_2 (PDF)

251 AUTHOR INFORMATION

252 Corresponding Authors

*e.w.meijer@tue.nl

*ron.naaman@weizmann.ac.il

253 ORCID

Andreas Vargas Jentsch: 0000-0003-1386-3174

E. W. Meijer: 0000-0003-4126-7492

254 Notes

The authors declare no competing financial interest.

260 ACKNOWLEDGMENTS

R.N. acknowledges discussion with Profs. Andrew Rapp and
David Waldeck and acknowledges partial support from the
European Research Council under the European Union's
Seventh Framework Program (FP7/2007-2013)/ERC grant
agreement no. [338720]. The Eindhoven laboratory acknowl-
edges financial support of EURO-SEQUENCES (H2020-
MSCA-ITN-2014, No 642083) and the FMS Gravitation
Program (No 024.001.035).

269 REFERENCES

- Gray, H. B. *Nat. Chem.* **2009**, *1* (1), 7.
- Ager, J. W.; Shaner, M. R.; Walczak, K. A.; Sharp, I. D.; Ardo, S. *Energy Environ. Sci.* **2015**, *8* (10), 2811–2824.
- Bard, A. J.; Fox, M. A. *Acc. Chem. Res.* **1995**, *28* (3), 141–145.
- Blankenship, R. E.; Tiede, D. M.; Barber, J.; Brudvig, G. W.; Fleming, G.; Ghirardi, M.; Gunner, M. R.; Junge, W.; Kramer, D. M.; Melis, A.; Moore, T. A.; Moser, C. C.; Nocera, D. G.; Nozik, A. J.; Ort, D. R.; Parson, W. W.; Prince, R. C.; Sayre, R. T. *Science* **2011**, *332* (6031), 805–809.
- Tachibana, Y.; Vayssieres, L.; Durrant, J. R. *Nat. Photonics* **2012**, *6* (8), 511–518.
- Reece, S. Y.; Hamel, J. A.; Sung, K.; Jarvi, T. D.; Esswein, A. J.; Pijpers, J. J. H.; Nocera, D. G. *Science* **2011**, *334* (6056), 645–648.
- Han, Z.; Eisenberg, R. *Acc. Chem. Res.* **2014**, *47* (8), 2537–2544.
- Yuhas, B. D.; Smeigh, A. L.; Douvalis, A. P.; Wasielewski, M. R.; Kanatzidis, M. G. *J. Am. Chem. Soc.* **2012**, *134* (25), 10353–10356.
- Fujishima, A.; Honda, K. *Nature* **1972**, *238* (5358), 37–38.

- 287 (10) Seabold, J. A.; Choi, K.-S. *Chem. Mater.* **2011**, *23* (5), 1105–1112.
- 289 (11) Kohl, S. W.; Weiner, L.; Schwartsburd, L.; Konstantinovski, L.; Shimon, L. J. W.; Ben-David, Y.; Iron, M. A.; Milstein, D. *Science* **2009**, *324* (5923), 74–77.
- 292 (12) Sivula, K.; Le Formal, F.; Grätzel, M. *ChemSusChem* **2011**, *4*, 293–449.
- 294 (13) Brillet, J.; Cornuz, M.; Formal, F. Le; Yum, J.-H.; Grätzel, M.; Sivula, K. *J. Mater. Res.* **2010**, *25* (1), 17–24.
- 296 (14) Mayer, M. T.; Du, C.; Wang, D. *J. Am. Chem. Soc.* **2012**, *134* (30), 12406–12409.
- 298 (15) Siegbahn, P. E. M.; Crabtree, R. H. *J. Am. Chem. Soc.* **1999**, *121* (1), 117–127.
- 300 (16) McEvoy, J. P.; Gascon, J. A.; Batista, V. S.; Brudvig, G. W. *Photochem. Photobiol. Sci.* **2005**, *4* (12), 940–949.
- 302 (17) Tommos, C.; Tang, X.-S.; Warncke, K.; Hoganson, C. W.; Styring, S.; McCracken, J.; Diner, B. A.; Babcock, G. T. *J. Am. Chem. Soc.* **1995**, *117* (41), 10325–10335.
- 305 (18) Yamaguchi, K.; Yamanaka, S.; Isobe, H.; Tanaka, K.; Ueyama, N. *Int. J. Quantum Chem.* **2012**, *112*, 3849–3866.
- 307 (19) Bozoglian, F.; Romain, S.; Ertem, M. Z.; Todorova, T. K.; Sens, C.; Mola, J.; Rodríguez, M.; Romero, I.; Benet-Buchholz, J.; Fontrodona, X.; Cramer, C. J.; Gagliardi, L.; Llobet, A. *J. Am. Chem. Soc.* **2009**, *131* (42), 15176–15187.
- 311 (20) Mavros, M. G.; Tsuchimochi, T.; Kowalczyk, T.; McIsaac, A.; Wang, L.-P.; Van Voorhis, T. *Inorg. Chem.* **2014**, *53* (13), 6386–6397.
- 313 (21) Chrétien, S.; Metiu, H. *J. Chem. Phys.* **2008**, *129* (7), 74705.
- 314 (22) Torun, E.; Fang, C. M.; de Wijs, G. A.; de Groot, R. A. *J. Phys. Chem. C* **2013**, *117* (12), 6353–6357.
- 316 (23) Mtangi, W.; Kiran, V.; Fontanesi, C.; Naaman, R. *J. Phys. Chem. Lett.* **2015**, *6* (24), 4916–4922.
- 318 (24) *Annu. Rev. Phys. Chem.* **2015**, *66* (1), 263–281.
- 319 (25) Klein, J. H.; Schmidt, D.; Steiner, U. E.; Lambert, C. *J. Am. Chem. Soc.* **2015**, *137* (34), 11011–11021.
- 321 (26) Helmich, F.; Lee, C. C.; Nieuwenhuizen, M. M. L.; Gielen, J. C.; Christianen, P. C. M.; Larsen, A.; Fytas, G.; Leclère, P. E. L. G.; Schenning, A. P. H. J.; Meijer, E. W. *Angew. Chem., Int. Ed.* **2010**, *49*, 3939–3942.
- 325 (27) Helmich, F.; Lee, C. C.; Schenning, A. P. H. J.; Meijer, E. W. *J. Am. Chem. Soc.* **2010**, *132* (47), 16753–16755.
- 327 (28) Kiran, V.; Mathew, S. P.; Cohen, S. R.; Hernández Delgado, I.; Lacour, J.; Naaman, R. *Adv. Mater.* **2016**, *28*, 1957–1962.
- 329 (29) Xie, Z.; Markus, T. Z.; Cohen, S. R.; Vager, Z.; Gutierrez, R.; Naaman, R. *Nano Lett.* **2011**, *11* (11), 4652–4655.
- 331 (30) Moore, G. F.; Blakemore, J. D.; Milot, R. L.; Hull, J. F.; Song, H.; Cai, L.; Schmuttenmaer, C. A.; Crabtree, R. H.; Brudvig, G. W. *Energy Environ. Sci.* **2011**, *4* (7), 2389–2392.
- 334 (31) Li, Z.; Kong, C.; Lu, G. *J. Phys. Chem. C* **2016**, *120* (1), 56–63.
- 335 (32) Gu, B.; Kiwi, J.; Graetzel, M. In *Hydrogen Systems*; Pergamon, 1986; Vol. 1, pp 121–134.
- 337 (33) Hansen, W. N.; Kuwana, T.; Osteryoung, R. A. *Anal. Chem.* **1966**, *38* (13), 1810–1821.
- 339 (34) Linsebigler, A. L.; Lu, G.; Yates, J. T. *Chem. Rev.* **1995**, *95* (3), 735–758.
- 341 (35) Rossmeisl, J.; Qu, Z.-W.; Zhu, H.; Kroes, G.-J.; Nørskov, J. K. *J. Electroanal. Chem.* **2007**, *607* (1–2), 83–89.
- 343 (36) Jirkovský, J.; Makarova, M.; Krtil, P. *Electrochem. Commun.* **2006**, *8* (9), 1417–1422.